DENKA NATMIC TYPE-10T

Alkali-Free Powder Accelerator for Shotcrete

Description

DENKA NATMIC TYPE-10T is an alkali-free powder accelerator for sprayed concrete based on calcium sulfoaluminate and can be used in civil engineering works such as road and railway tunnels, headraces, and mines. The accelerator is applied where initial rock support is needed or where a permanent lining will be placed.

Features

- Quick setting time and high initial strength are performed through ettringite formation in the initial stage
- Development of high compressive strength after 28 days and excellent long-term durability
- Good bonding to the ground surface and low rebound
- Alkali free (Alkali ion content is less than 1%)

Typical applications

- Rock support in underground spaces (tunnels, headraces and mines)
- Slope stabilization

Technical data (Physical properties)

Color/Form	Grayish white/Powder		
Mass density (20 °C, g/cm³)	2.70–3.00		
Bulk density (20 °C, g/cm ³)	0.80–1.30		
Chlorine content (%)	<0.01		
Alkali content (Na₂O equiv. %)	<1		

Packaging

• 25 kg bags


Mix proportions and accelerator-dosing position

W/C s/a	Unit content (kg/m³)			SP	NATMIC TYPE-10T		
	S/a	Water	Cement	Sand	Gravel	(Cement×%)	(Cement×%)
0.45	0.60	189	420	1065	716	1.2	10

- W/C:Water-cement ratio, s/a:Sand-aggregate (sand and gravel) ratio
- · Cement: ordinary Portland cement
- SP: Superplasticizer based on polycarboxylate



- The dosage of DENKA NATMIC TYPE-10T depends on the temperature, cement reactivity, setting time, strength development, and required thickness of the layers.
- The dosage of DENKA NATMIC TYPE-10T ranges from 6% to 12% of the cement weight.
- The cement weight per cubic meter should exceed 380 kg/m³ and preferably be no less than 400 kg/m³.
- The water to cement ratio should be below 0.5 and preferably no more than 0.45.
- The hose length between the nozzle and the dosing position of the accelerator should be 1.0–1.5 m.
- When DENKA NATMIC TYPE-10T is used for concrete containing fly ash and/or silica fume, the setting speed is higher than that for cement only. Therefore, the hose length between the nozzle and the dosing position of the accelerator should be less than 0.5m

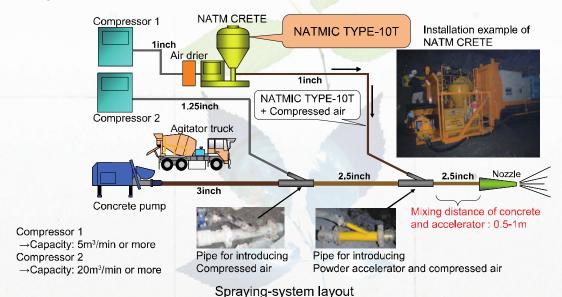

Technical data (Setting and strength development)

1) Setting properties of accelerating mortar (example data)

Dosage of	Initial setting	Final setting	<mixing mortar="" of="" proportion=""></mixing>
accelerator (%)	(minsec.)	(minsec.)	Temperature : 20 °C
8	2-35	9-45	Water/cement ratio = 0.45
10	2-20	7-50	Cement : sand mass ratio = 1:2.5 Dosage of superplasticizer : 1.2%
12	2-15	5-22	(vs. cement)

2) Compressive strength development of sprayed concrete (example data)

Compressive strength (MPa)							
3 hours	8 hours	1 day	3 days	7 days	28 days		
2.5	8.0	17	27	34	42		

- This results were obtained in a spraying test using the wet-mix sprayed concrete having the above mixing proportion (Section 6).
- Properties of fresh concrete before spraying are slump of 195 mm and air content of 1.7%
- Compressive strengths after 3 hours, 8 hours and 1 day were estimated in a pull-out test
- Other compressive strengths were measured with a cylindrical specimen that was extracted by drilling from hardened sprayed concrete



Precautions when handling

- Refer to the Safety Data Sheet (SDS) before use.
- Before spraying work, check the spraying system for abnormalities (e.g., check the piping, check for deterioration of the hose, and ensure the correct operation of all equipment).
- Optimize the dosage and dosing position of the product for the spraying process after spraying trials.
- Wear protective clothing and equipment (e.g., goggles, mask, gloves, and rubber boots) during handling.
- If piping is blocked with concrete or accelerator, clean the piping after completely releasing pressurized air from the piping. Do not look into the inside a hose.
- Do not dispose of DENKA NATMIC TYPE-10T drains.
- Keep the product in a place with low humidity when possible.
- The product in open bags should be used up completely or the bag should be resealed for storage.
- Use accelerator dosing equipment (DENKA NATMCRETE).
- For further information, please contact DENKA.

Limitation of liability

- The information contained in this document is general advice for potential DENKA customers about the basic properties and characteristics of various DENKA products (hereafter referred to as "the Product Information"). DENKA provides no warranty and makes no representation as to the complete accuracy or completeness of the Product Information in this brochure.
- Nothing in this brochure will be deemed to provide any expressed or implied warranty or obligation of DENKA with respect to the Product Information or its use, including, but not limited to, any warranty of merchantability, suitability for a particular purpose, or infringement of any intellectual property rights.
- Any user of the Product Information and DENKA products is responsible for properly determining
 the manner and suitability of use of the Product Information and DENKA products in their own
 operations. The user should exercise proper care in considering the Material Safety Data Sheet,
 Product Information and any other technical information provided by DENKA, including
 descriptions of conditions of use, warnings, and cautionary instructions.
- DENKA reserves the right to change the Product Information from time to time at its discretion and without notice.



DENKI KAGAKU KOGYO K.K.

Special Cement Additives Department
TEL: +81-3-3507-5465 FAX: +81-3-3507-5085

-China-DENKA INFRASTRUCTURE TECHNOLOGIES SHANGHAI

ROOM 2807, NEW HONGQIAO CENTER BLDG

NO.83 LOUSHANGUAN RD, CHANG NING AREA, SHANGHAI CHINA

TEL: +86-21-6236-5510 FAX: +86-21-6236-5505 -Asia-DENKA INFRASTRUCTURE TECHNOLOGIES PTE LTD

4 SHENTON WAY #29-02 SGX CENTRE 2 SINGAPORE 068807 TEL:+65-6216-0580

TEL:+65-6216-0580 FAX:+65-6224-3840 -Europe-DENKA CHEMICALS GMBH

WEHRHAHN-CENTER, CANTADOR STR.3, DUSSELDORF, GERMANY TEL: +49-211-130990

FAX: +49-211-329942